
AD-A055 966 ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND WATER--ETC F/G 19/1
FEASIBILITY STUDY OF FILAMENT WOUND CARTRIDGE CASES.(U)
MAR 78 G D'ANDREA, R CULLINAN, P CROTEAU

UNCLASSIFIED ARLCB-MR-78007 SBIE-AD-E440 007 NL

1 OF 1
ADA
065966

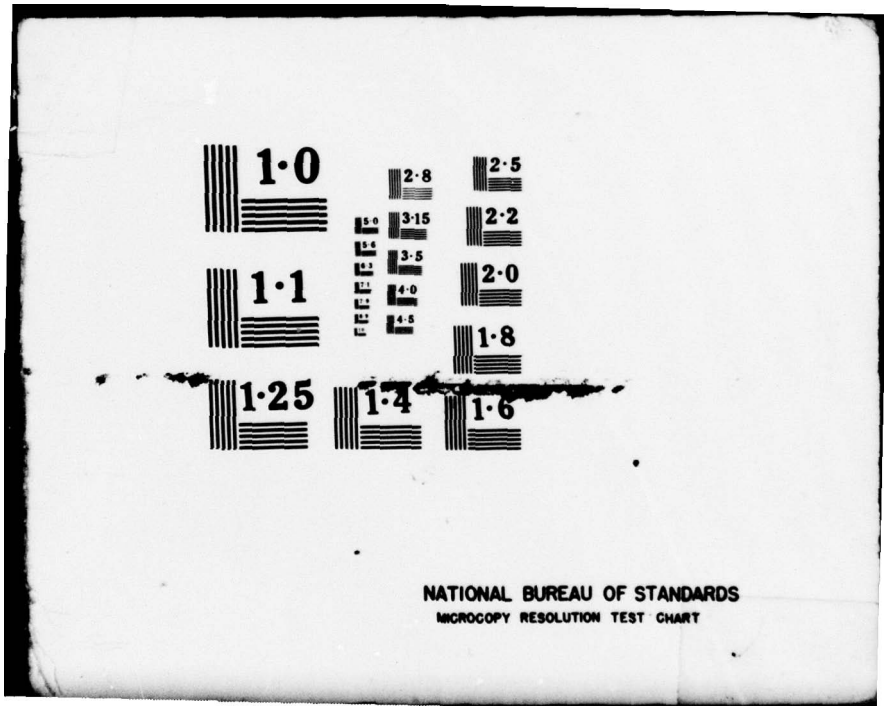

END
DATE
FILMED
8-78
DDC


1·0
1·1
1·25
2·8
3·15
3·5
4·0
4·5
1·4
2·5
2·2
2·0
1·8
1·6
NATIONAL BUREAU OF STANDARDS
MICROCOPY RESOLUTION TEST CHART

AD A055966

6-6-78

LEVEL II

12 B.S.

19 AD-E440 107

18 SBIE

14 ARLCB-MR-78007

6 FEASIBILITY STUDY OF FILAMENT WOUND CARTRIDGE CASES.

9 Memorandum rept.,

10 G. D'Andrea
R. Cullinan
P. Croteau

11 March 1978 12 17p.

US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND
LARGE CALIBER WEAPON SYSTEMS LABORATORY
BENÉT WEAPONS LABORATORY
WATERVLIET, N. Y. 12189

16 AMCMS No. 611101.91A0011
DA Project No. 1T161101A91A
PRON No. 1A-7-233A3-GG-M7

DDC RECEIVED JUL 6 1978 B

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

AD No. ____
DDC FILE COPY

393417 410224 mt

6-13-78 telecon w/ Pat Altnar (ARRADCOM - Dover); the TM report series is not valid & the change is being made to MR. J. LaChance DDC-TCA-2

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

DISPOSITION

Destroy this report when it is no longer needed. Do not return it to the originator.

CHANGE NOTICE

TECHNICAL MEMORANDUM ARLCB-TM-78007

FEASIBILITY STUDY OF FILAMENT WOUND CARTRIDGE CASES

ERRATA SHEET
(Change Notice)

C1 19 June 1978

The following (pen & ink) changes should be made to the above subject publication:

Front Cover - Change TECHNICAL MEMORANDUM ARLCB-TM-78007 to read MEMORANDUM REPORT ARLCB-MR-78007

DD Form 1473 - Change ARLCB-TM-78007 to read ARLCB-MR-78007

US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND

LARGE CALIBER WEAPON SYSTEMS LABORATORY

BENÉT WEAPONS LABORATORY

WATERVLIET, N. Y. 12189

SECURITY CLASSIFICATION OF THIS PAGE *(When Data Entered)*

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER ARLCB-MR-78007	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE *(and Subtitle)* FEASIBILITY STUDY OF FILAMENT WOUND CARTRIDGE CASES		5. TYPE OF REPORT & PERIOD COVERED 6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) G. D'Andrea R. Cullinan P. Croteau		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS Benet Weapons Laboratory Watervliet Arsenal, Watervliet, N.Y. 12189 DRDAR-LCB-TL		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AMCMS No. 611101.91A0011 DA Proj. No. 1T161101A91A PRON No. 1A-7-233A3-GG-M7
11. CONTROLLING OFFICE NAME AND ADDRESS US Army Armament Research and Development Command Large Caliber Weapon Systems Laboratory Dover, New Jersey 07801		12. REPORT DATE March 1978 13. NUMBER OF PAGES 18
14. MONITORING AGENCY NAME & ADDRESS *(if different from Controlling Office)*		15. SECURITY CLASS. *(of this report)* UNCLASSIFIED 15a. DECLASSIFICATION/DOWNGRADING SCHEDULE

16. DISTRIBUTION STATEMENT *(of this Report)*

Approved for public release; distribution unlimited.

17. DISTRIBUTION STATEMENT *(of the abstract entered in Block 20, if different from Report)*

18. SUPPLEMENTARY NOTES

19. KEY WORDS *(Continue on reverse side if necessary and identify by block number)*

Cartridge Cases
Composites
Filament Winding

20. ABSTRACT *(Continue on reverse side if necessary and identify by block number)*

The feasibility of fabricating a 60mm composite cartridge case by the filament winding process has been demonstrated. Fabrication procedures for the manufacturing of this type of case are presented in this report.

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE


SECURITY CLASSIFICATION OF THIS PAGE *(When Data Entered)*

TABLE OF CONTENTS

	Page
INTRODUCTION	1
FABRICATION	1
CONCLUSIONS	5

LIST OF ILLUSTRATIONS

Figure 1.	Drawing of Mandrel Used in Fabricating Fiberglass Cases.	7
Figure 2.	Output from GEOD Showing: A. Schematic of Mandrel's Geometry B. Angle of Wrap vs Mandrel Length C. Proper Winding Program for Winding Machine	8
Figure 3.	Machining Drawing for Case 60-1.	9
Figure 4.	Machining Drawing for Case 60-2.	10
Figure 5.	Final Machining Drawing for Cases 60-3 and 60-4.	11
Figure 6.	Finish Machined Case 60-4 with the Mandrel.	12
Figure 7.	View of the Simulated Projectile, Fiberglass Case, and the Steel Stub Case.	13
Figure 8.	Assembled View of Projectile, Cartridge Case, and Stub Case.	14

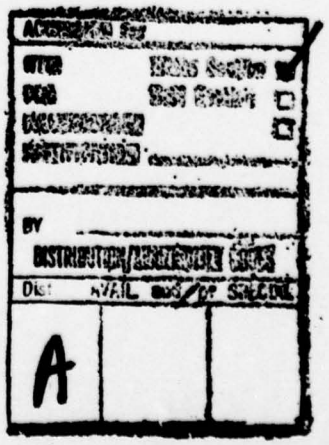

INTRODUCTION

The combustible cartridge case, as proposed for use in such weapons as the 60mm automatic cannon, has, on occasions, shown (a) the disadvantage of being structurally incapable of with standing the stresses during the loading cycle, and (b) intolerance to burning residue products, and high chamber surface temperature.

This report introduces a novel cartridge case made of fiber-glass-epoxy material which is expected to be free of these problems.

This approach appears feasible in that: (a) there should be no automatic loading and/or extraction problems as the fiberglass composite has a specific strength 3 times higher than conventional gun steels, with a specific modulus similar to the steels, (b) the fiberglass will act as a thermal insulator against any hot gases or burning residue left in the chamber from a previous round and/or high chamber surface temperature, and (c) the approach is also practical since the proposed case can be easily manufactured.

FABRICATION

The procedures for tailoring the composite's properties to a specific application are well understood. Automatic winding machinery, computer controlled, has been used to fabricate a total of four 60mm cartridge cases made of prepreg "S" glass/epoxy. All cases were wound on a hard coated aluminum (6061) mandrel which was machined to the dimensions shown in Figure 1. The curing cycle of the resin called for 1 hour at 200°F and 2 hours at 350°F.

Figure 2, which is a computer printout, shows a schematic of the mandrel's geometry (A) which is imput to the computer program GEOD. It also shows (B) the angle of wrap of the helical winding as it traverses the length of the mandrel. This data is important in determining the strength properties of the case at various points along its length.

GEOD is the computer program that provides the proper program (C) for the Winding Machine. Given the mandrel's geometry, GEOD outputs the helical winding program that will provide the proper geodesic (non-slip) filament path.

Case 60-1

The first case wound was fabricated to meet the dimensions shown in Figure 3. This case was thin walled like the disposable cartridge case it was to replace. Four helical patterns (8 layers) were required to meet the 0.085 in. wall.

Most of the case was left in the "as wound" condition with finish machining required at the base (where case slips into steel stub) and the nose (where the helical wrap on a smaller diameter causes excessive build-up) to meet the requirements of Figure 3. A later decision was made to go with a thicker walled case, therefore, this sample could not be used. It was, however, cut in half along its length so that a better view of the dome build-up was obtained.

Although lightweight, fiberglass case could never match the weight of the ultra-light disposable case, and this was never one of the requirements. Sample 60-1, which was fabricated and machined to the approximate geometry of the disposable case weighed over 500 gms while the disposable case weighs ~ 250 gms. Since ultra light-weight was not a criteria, it was decided that the fiberglass case be made thicker walled. This was done to reduce the clearance between the case and the chamber wall from ~ .070 in. to ~ .004 in. This effect would greatly reduce the deflection of the fiberglass case which in return would minimize the stress concentration at the shoulder where the case fits into the steel stub case. In addition, the new clearance would assure that the fiberglass case would stay within its plastic zone upon pressurization. Both of these conditions would assure easy extraction of the case.

Case 60-2

This case was wound to meet the thicker-walled dimensions shown in Figure 4. Four helical patterns were again used but in order to meet the thick-wall dimension of .143 in., eight additional hoop layers were wound on the body of the case from the base end to a point ½ in. down the dome.

This case was machined similar to 60-1, with finish machining at the base and dome sections only. Some hand finishing was required to obtain the smooth contour on the dome.

The O.D. dimensions shown in Figure 4 were to provide for the .004 radial clearance between the case and the expected chamber dimensions. This case was matched with a steel stub case and the assembly was inserted

into the chamber of a 60mm tube. The case assembly did not seal and it hung up at the top of the dome. It was thought that the hand finishing on this dome did not remove enough material and was therefore oversize.

It was decided at this time to fabricate an oversize fiberglass case that would be machined entirely on a numerically controlled (NC) lathe. This would assure exact control and assure that the case met specifications especially in the area of domes.

Case 60-3

This sample was wound oversize to provide enough material for NC machining of the entire case to the dimensions shown in Figure 4. Six helical patterns were wound along with an additional 6 hoop layers on the body of the case.

A machining program was prepared and the case was finish machined on a NC lathe. This case was matched with a steel stub and inserted into the chamber. This assembly also did not seal in the chamber and again the hang-up was at the top of the dome.

The case was then given a detailed inspection on a comparator and found to be within the tolerances of Figure 4. A detailed examination of the tube's machining operations finally ascertained the problem. Extremely generous radius tolerances (1.0 in. on the converging radius and 1.0 in. on the diverging radius) resulted in a chamber converging and diverging radii of 2.50"R. A look at Figure 4, which illustrates the case's matching dimensions at these locations shows why this case and #60-2 did not seal. The O.D. of the case was remachined to 2.88"R at the converging radius and 3.00"R at the diverging radius. The remachined case with another stub case was inserted in the chamber and resulted in a perfect fit.

Case 60-4

This final fiberglass case was wound exactly as #60-3. It was NC machined to the dimensions shown in Figure 5 and this case, with a steel stub case fit exactly in the chamber.

Figure 6 is a view of the finish machined case (60-4) with the hard-coated Aluminum mandrel. Still attached to the mandrel are the "as wound" fiberglass end caps. Figure 7 shows the simulated projectile, fiberglass cartridge case, and the steel stub case. The steps shown at the base of the cartridge case slide into two mating shoulders inside the stub case. This concept calls for bonding these surfaces with a high strength adhesive after loading.

An overall assembled view of the projectile, cartridge case, and steel stub case is shown in Figure 8. This finished round is to be tested in the test firing of the MCAAAC gun system.

CONCLUSIONS

The feasibility of fabricating a composite cartridge case by the filament winding process has been demonstrated. Future work should include:

A. The study of the interaction between the cartridge case and gun barrel chamber. This study could be an extension of the work done by Frankford Arsenal on the "Three Dimensional Finite Element Analysis on the 20mm Cartridge Case, M204 and M139 Gun" (Oct 1975) and "Application of NASTRAN in Non-Linear Analysis of the Cartridge Case Neck Separation Malfunction" (Oct 1975). The study will investigate the deformation and stresses that are developed in the cartridge case as it is seated in the barrel chamber, and the displacements and stresses caused by a subsequent pressure loading.

B. The study of fabrication procedures to wind repeatable geodesic paths for optimum structural properties.

C. Test firings to ascertain the structural integrity of the composite cartridge case.

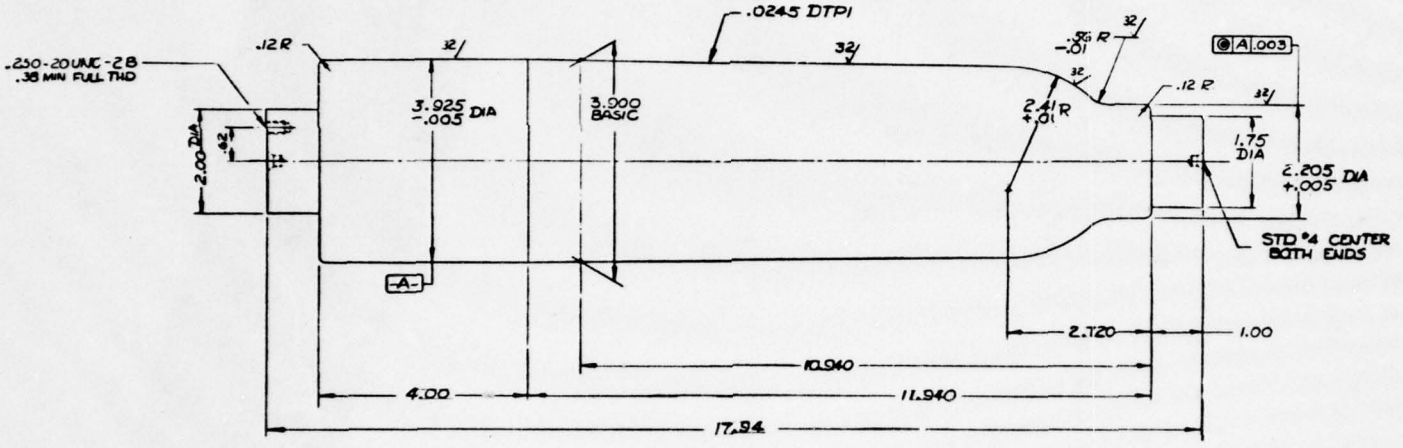


Figure 1. Drawing of mandrel used in fabricating fiberglass cases.

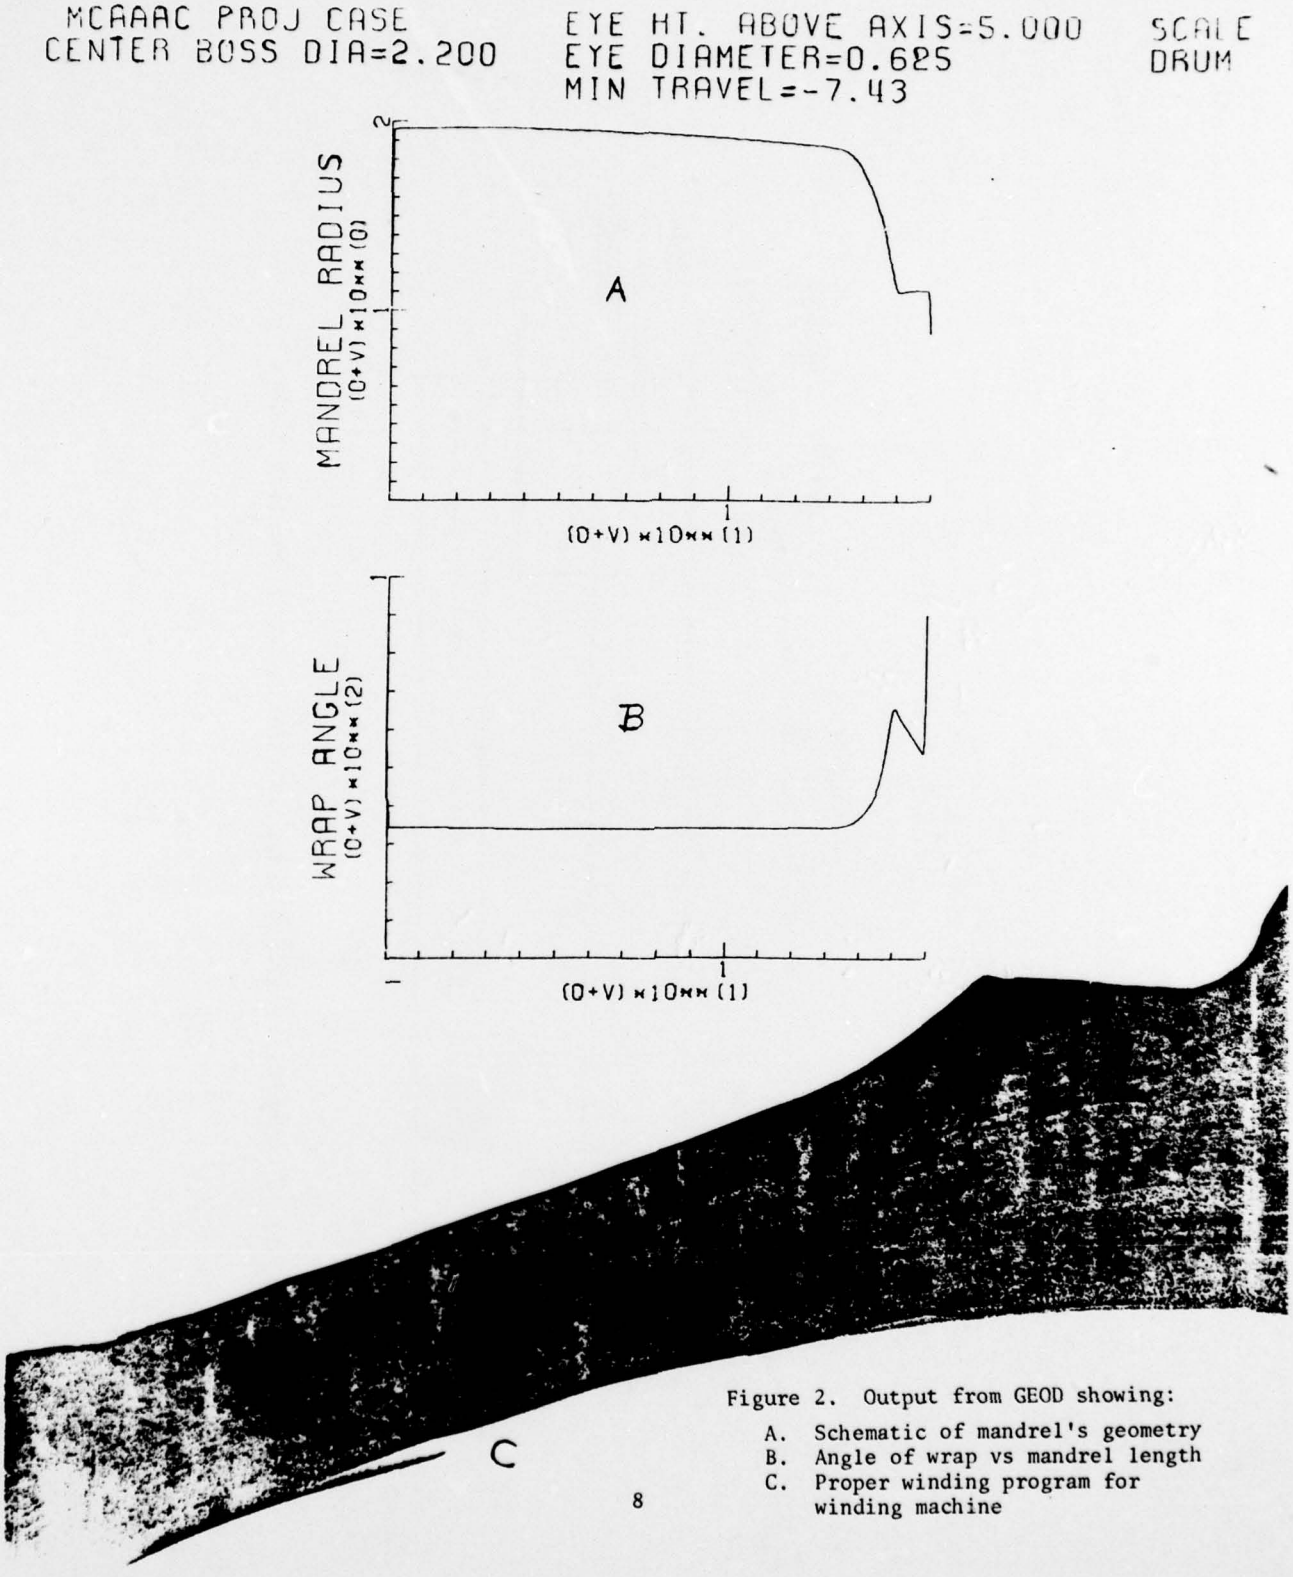


Figure 2. Output from GEOD showing:

A. Schematic of mandrel's geometry
B. Angle of wrap vs mandrel length
C. Proper winding program for winding machine

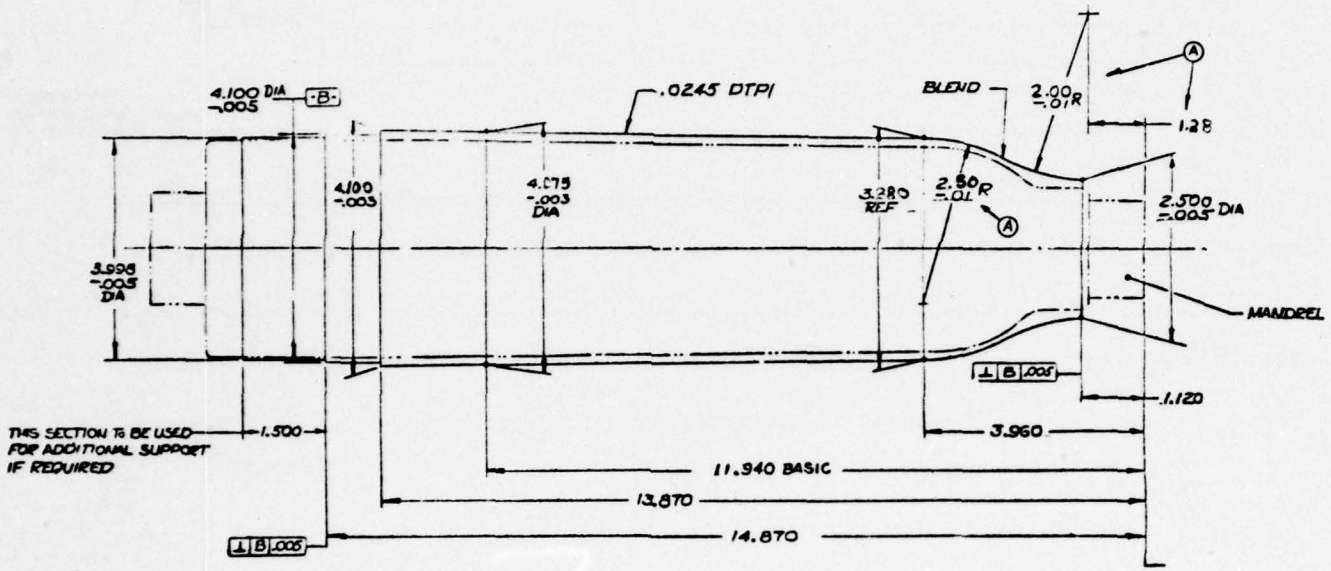


Figure 3. Machining drawing for case 60-1.

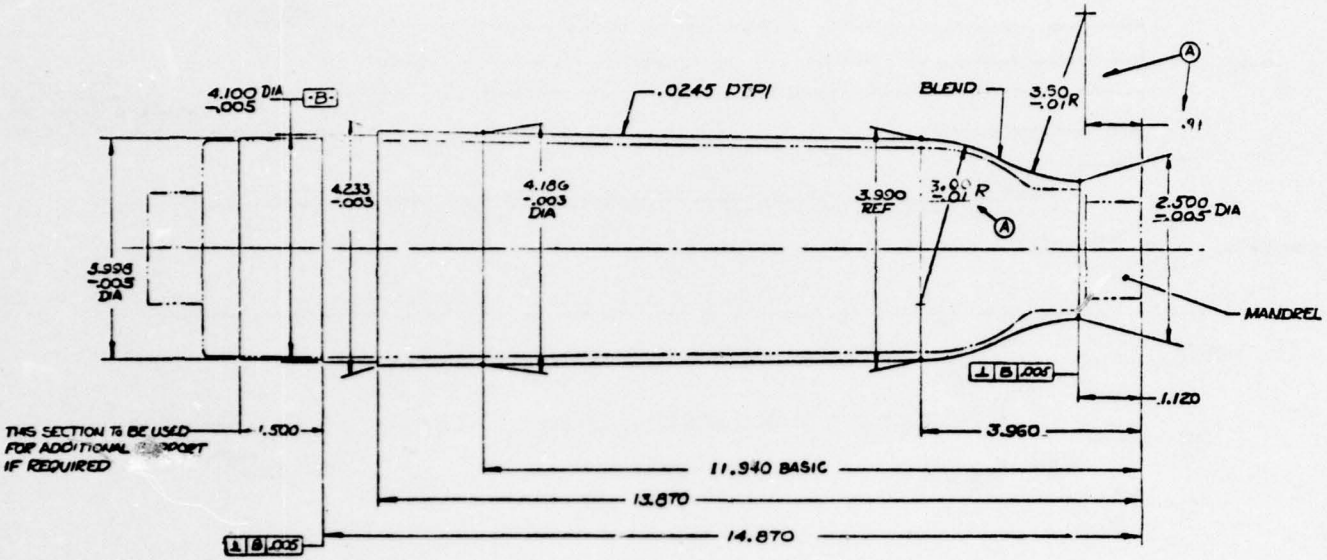


Figure 4. Machining drawing for case 60-2.

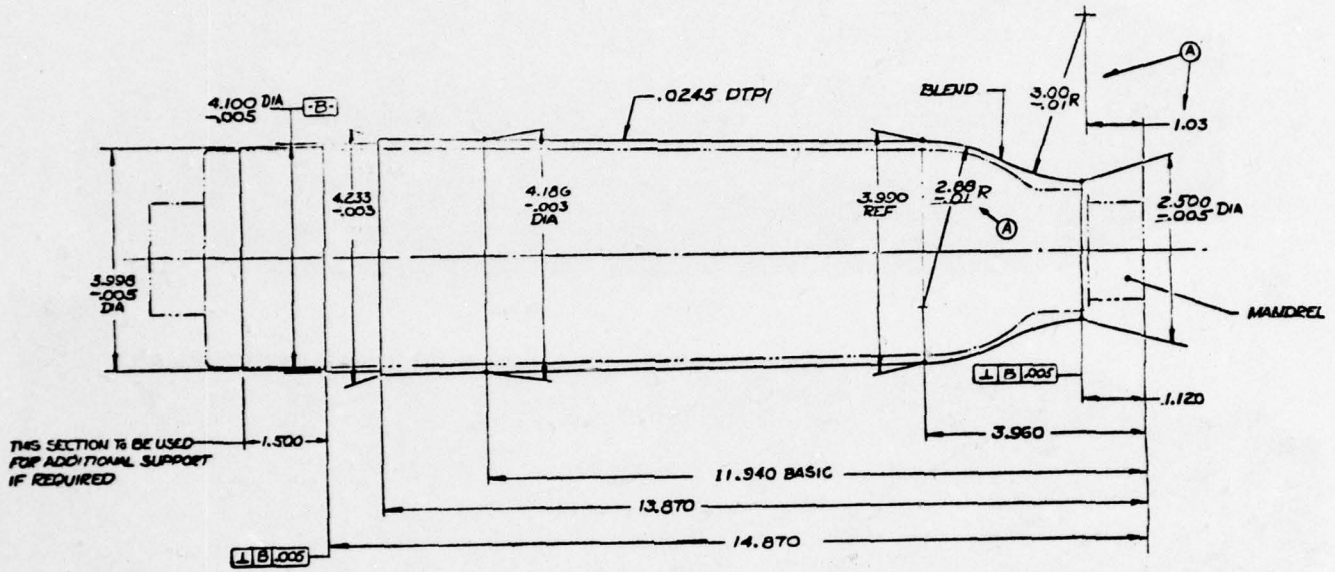


Figure 5. Final machining drawing for cases 60-3 and 60-4.

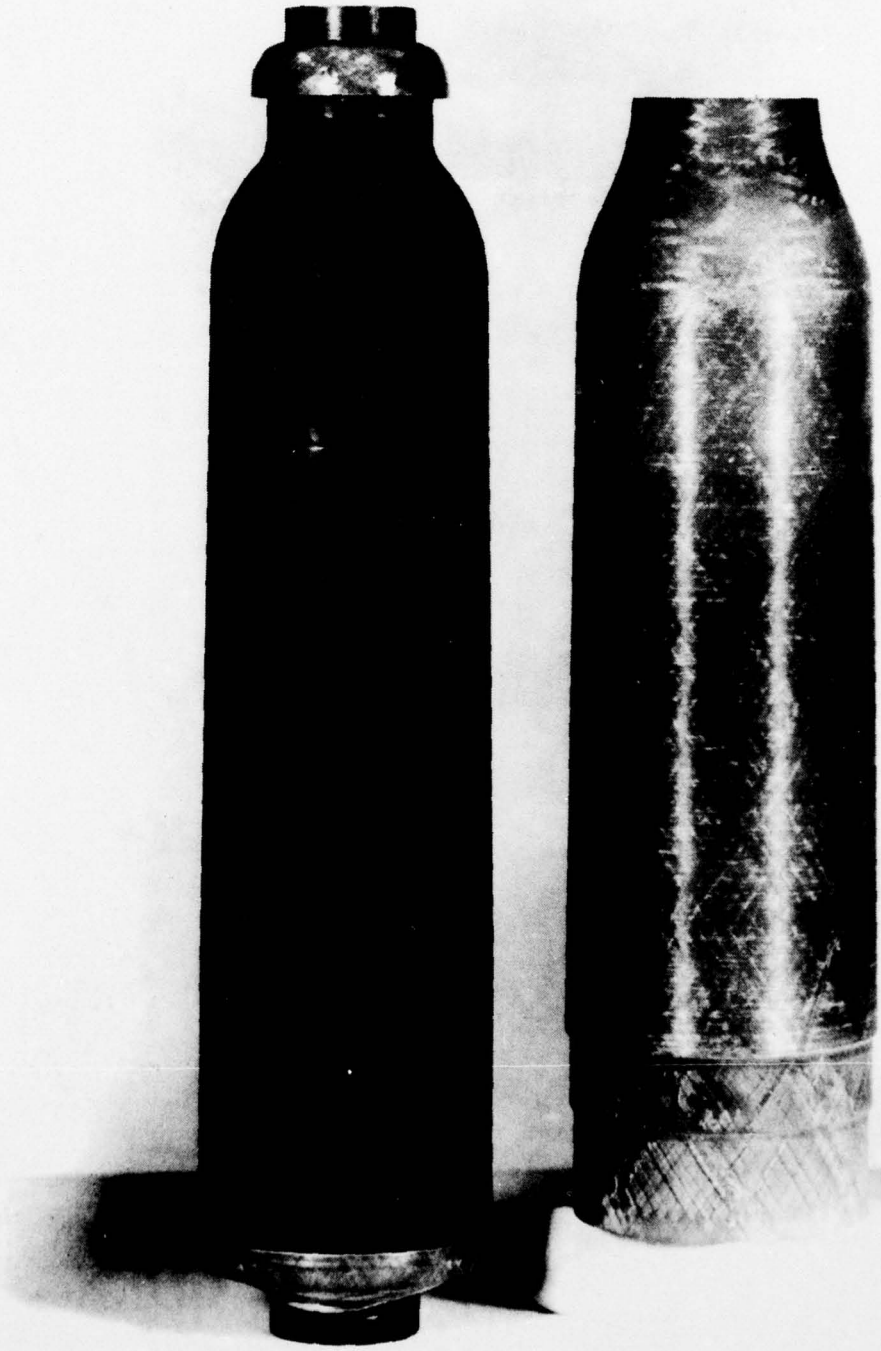


Figure 6. Finish machined case 60-4 with the mandrel.

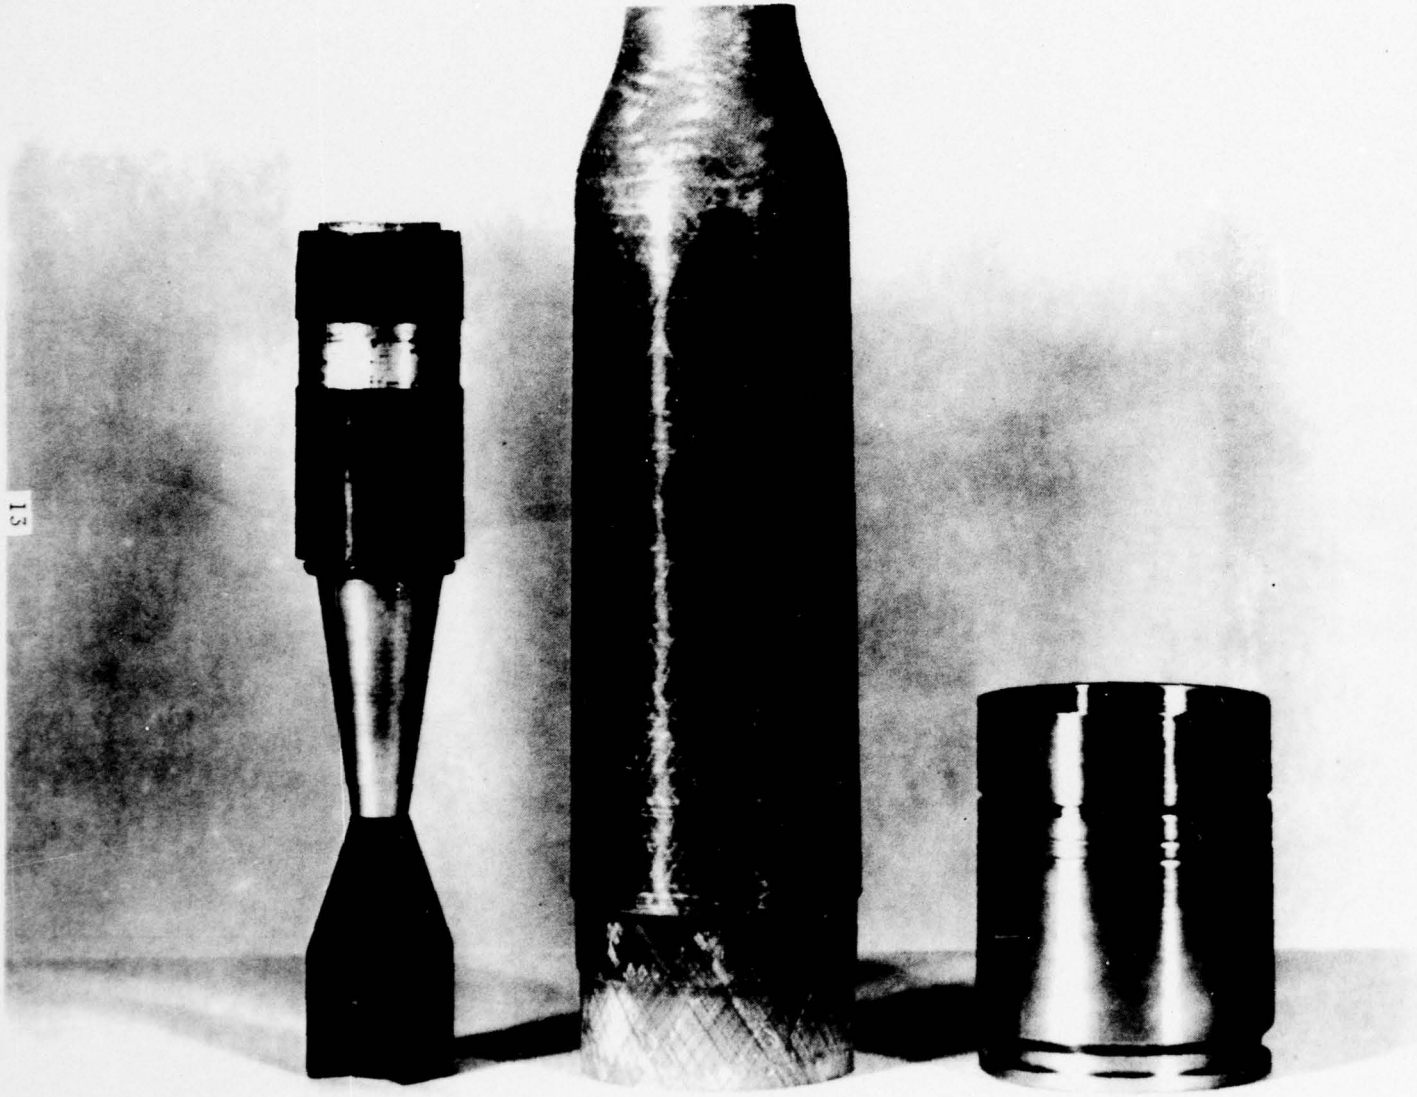


Figure 7. View of the simulated projectile, fiberglass case, and the steel stub case.

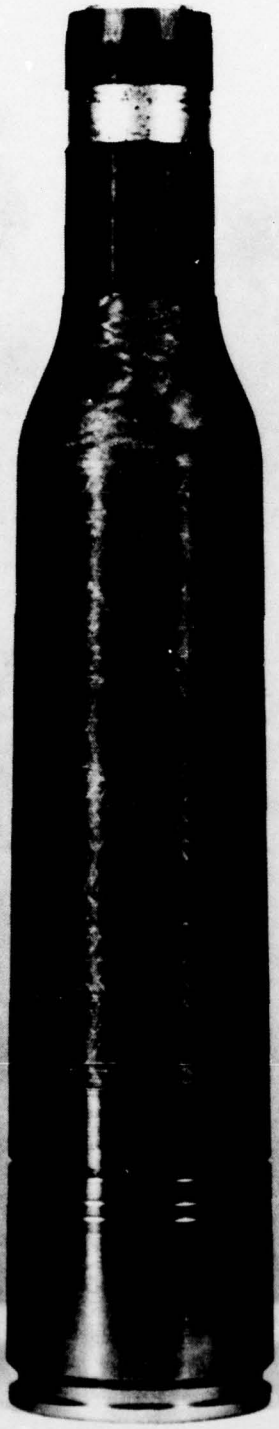


Figure 8. Assembled view of projectile, cartridge case, and stub case.

WATERVLIET ARSENAL INTERNAL DISTRIBUTION LIST

May 1976

	No. of Copies
COMMANDER	1
DIRECTOR, BENET WEAPONS LABORATORY	1
DIRECTOR, DEVELOPMENT ENGINEERING DIRECTORATE	1
ATTN: RD-AT	1
RD-MR	1
RD-PE	1
RD-RM	1
RD-SE	1
RD-SP	1
DIRECTOR, ENGINEERING SUPPORT DIRECTORATE	1
DIRECTOR, RESEARCH DIRECTORATE	2
ATTN: RR-AM	1
RR-C	1
RR-ME	1
RR-PS	1
TECHNICAL LIBRARY	5
TECHNICAL PUBLICATIONS & EDITING BRANCH	2
DIRECTOR, OPERATIONS DIRECTORATE	1
DIRECTOR, PROCUREMENT DIRECTORATE	1
DIRECTOR, PRODUCT ASSURANCE DIRECTORATE	1
PATENT ADVISORS	1

EXTERNAL DISTRIBUTION LIST

December 1976

1 copy to each

OFC OF THE DIR. OF DEFENSE R&E
ATTN: ASST DIRECTOR MATERIALS
THE PENTAGON
WASHINGTON, D.C. 20315

CDR
US ARMY TANK-AUTMV COMD
ATTN: AMDTA-UL
AMSTA-RKM MAT LAB
WARREN, MICHIGAN 48090

CDR
PICATINNY ARSENAL
ATTN: SARPA-TS-S
SARPA-VP3 (PLASTICS TECH EVAL CEN)
DOVER, NJ 07801

CDR
FRANKFORD ARSENAL
ATTN: SARFA
PHILADELPHIA, PA 19137

DIRECTOR
US ARMY BALLISTIC RSCH LABS
ATTN: AMXBR-LB
ABERDEEN PROVING GROUND
MARYLAND 21005

CDR
US ARMY RSCH OFC (DURHAM)
BOX CM, DUKE STATION
ATTN: RDRD-IPL
DURHAM, NC 27706

CDR
WEST POINT MIL ACADEMY
ATTN: CHMN, MECH ENGR DEPT
WEST POINT, NY 10996

CDR
HQ, US ARMY AVN SCH
ATTN: OFC OF THE LIBRARIAN
FT RUCKER, ALABAMA 36362

CDR
US ARMY ARMT COMD
ATTN: AMSAR-PPW-IR
AMSAR-RD
AMSAR-RDG
ROCK ISLAND, IL 61201

CDR
US ARMY ARMT COMD
FLD SVC DIV
ARMCOM ARMT SYS OFC
ATTN: AMSAR-ASF
ROCK ISLAND, IL 61201

CDR
US ARMY ELCT COMD
FT MONMOUTH, NJ 07703

CDR
REDSTONE ARSENAL
ATTN: AMSMI-RRS
AMSMI-RSM
ALABAMA 35809

CDR
ROCK ISLAND ARSENAL
ATTN: SARRI-RDD
ROCK ISLAND, IL 61202

CDR
US ARMY FGN SCIENCE & TECH CEN
ATTN: AMXST-SD
220 7TH STREET N.E.
CHARLOTTESVILLE, VA 22901

DIRECTOR
US ARMY PDN EQ. AGENCY
ATTN: AMXPE-MT
ROCK ISLAND, IL 61201

EXTERNAL DISTRIBUTION LIST (Cont)

1 copy to each

CDR
US NAVAL WPNS LAB
CHIEF, MAT SCIENCE DIV
ATTN: MR. D. MALYEVAC
DAHLGREN, VA 22448

DIRECTOR
NAVAL RSCH LAB
ATTN: DIR. MECH DIV
WASHINGTON, D.C. 20375

DIRECTOR
NAVAL RSCH LAB
CODE 26-27 (DOCU LIB.)
WASHINGTON, D.C. 20375

NASA SCIENTIFIC & TECH INFO FAC
PO BOX 8757, ATTN: ACQ BR
BALTIMORE/WASHINGTON INTL AIRPORT
MARYLAND 21240

DEFENSE METALS INFO CEN
BATTELLE INSTITUTE
505 KING AVE
COLUMBUS, OHIO 43201

MANUEL E. PRADO / G. STISSER
LAWRENCE LIVERMORE LAB
PO BOX 808
LIVERMORE, CA 94550

DR. ROBERT QUATTRONE
CHIEF, MAT BR
US ARMY R&S GROUP, EUR
BOX 65, FPO N.Y. 09510

2 copies to each

CDR
US ARMY MOB EQUIP RSCH & DEV COMD
ATTN: TECH DOCU CEN
FT BELVOIR, VA 22060

CDR
US ARMY MAT RSCH AGCY
ATTN: AMXMR - TECH INFO CEN
WATERTOWN, MASS 02172

CDR
WRIGHT-PATTERSON AFB
ATTN: AFML/MXA
OHIO 45433

CDR
REDSTONE ARSENAL
ATTN: DOCU & TECH INFO BR
ALABAMA 35809

12 copies

CDR
DEFENSE DOCU CEN
ATTN: DDC-TCA
CAMERON STATION
ALEXANDRIA, VA 22314

NOTE: PLEASE NOTIFY CDR, WATERVLIET ARSENAL, ATTN: SARWV-RT-TP, WATERVLIET, N.Y. 12189, IF ANY CHANGE IS REQUIRED TO THE ABOVE.